

	SURFACE VEHICLE RECOMMENDED PRACTICE		J1523 FEB2012
		Issued	1985-06
		Revised	2012-02
		Superseding J1523 NOV1993	
(R) Metal to Metal Overlap Shear Strength Test for Automotive Type Adhesives			

RATIONALE

This document contains minor changes, such as additional references, to better reflect current practices.

1. SCOPE

This SAE Recommended Practice defines a procedure for determining shear strengths of adhesives used for bonding automotive oil metal substrates.

2. REFERENCES

2.1 Applicable Documents

The following publications form a part of this specification to the extent specified herein. Unless otherwise indicated, the latest issue of SAE publications shall apply.

2.1.1 ASTM Publication

Available from ASTM International, 100 Barr Harbor Drive, P.O. Box C700, West Conshohocken, PA 19428-2959, Tel: 610-832-9585, www.astm.org

ASTM D 1002 Test Method for Strength Properties of Adhesives in Shear by Tension Loading (Metal-to-Metal)

ASTM D 4896 Guide for Use of Adhesive-Bonded Single Lap-Joint Specimens

3. TEST SUBSTRATES

3.1 Substrates

Metal composition and roughness as specified.

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be revised, reaffirmed, stabilized, or cancelled. SAE invites your written comments and suggestions.

Copyright © 2012 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
 Tel: +1 724-776-4970 (outside USA)
 Fax: 724-776-0790
 Email: CustomerService@sae.org
 SAE WEB ADDRESS: <http://www.sae.org>

**SAE values your input. To provide feedback
 on this Technical Report, please visit
http://www.sae.org/technical/standards/J1523_201202**

3.2 Dimensions

Metal substrates shall be cut into flat coupons 25 mm (1.0 in) x 100 mm (4.0 in) at 0.8 mm (0.030 in) nominal thickness unless otherwise specified. Coupons shall be free from burrs or other surface imperfections.

3.3 Surface Preparation

Remove contaminant from test coupon surface using a neutral solvent such as acetone or methyl ethyl ketone. Apply a uniform 0.025 mm (0.001 in) wet thickness coating of light mineral oil over test coupons unless otherwise specified. Condition coupons at $23\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$ and $50\% \pm 5\%$ humidity for 1 h minimum before bonding.

4. PREPARATION OF TEST JOINTS

4.1 Joint Geometry

Joint geometry will be as shown in Figure 1. A 3.2 cm^2 (0.5 in^2) overlap is recommended.

4.2 Adhesive Bondline Thickness

Evaluate adhesive bondline thickness at 0.25 mm (0.010 in) unless otherwise specified. Bondline thickness can be controlled by inserting wire or glass bead spacers into the adhesive. The spacer volume shall not exceed 1% of the total adhesive volume.

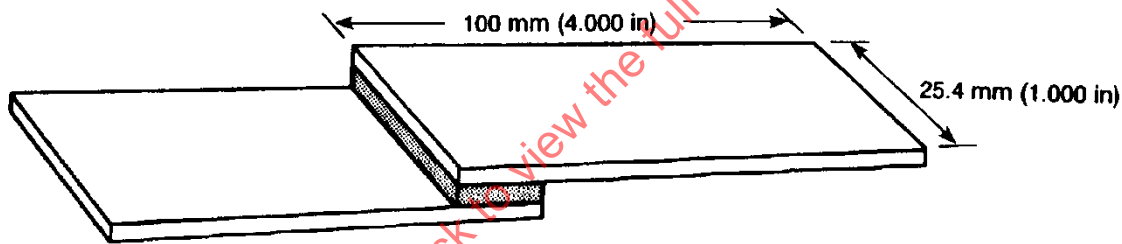


FIGURE 1 - JOINT GEOMETRY

4.3 Adhesive Application

The quantity of adhesive used to prepare the bond should be regulated to avoid excess squeeze-out. Squeeze-out at the edges of the bond shall be removed prior to curing.

4.4 Clamping and Fixturing

Bonding surfaces shall be firmly fixed and retained through cure cycle.

4.5 Adhesive Cure

Adhesive shall be cured in accordance with the adhesive suppliers or automotive engineer's recommendation.

4.6 Conditioning

Bonded specimens shall be allowed to return to ambient temperatures for 1 h minimum prior to testing.